



**METALLURGICA
SAN MARCO**

DATA SHEET: CW625N

HOT FORGING

aggiornato al 06 / 23

ALLOY: CW625N

Anti-dezincification alloy with low lead content.

ALLOY DESIGNATION

UNIEN: CW625N - CuZn35Pb1.5AlAs

CHEMICAL COMPOSITION UNI EN12165 ED.2016

Cu	Pb	Sn	Fe	Ni	Al	Mn	As	Zn	Other elements
min.62.0% max 64.0%	1.2% 1.6%	≤0.3 %	≤0.3 %	≤0.2 %	≤0.5 % ≤0.7 %	≤0.1 %	0.02 % 0.15 %	difference	≤0.2 %

Each unnamed element must be ≤0.02%.

Restriction group of the surface in contact with drinking water according to the "Common composition list": B and D

HEAT TREATMENTS

Two types of heat treatments are recommended to be carried out according to one's needs

STRESS RELIEVING

It specifically allows redistribution of tension induced by machining or cold plastic deformation, reducing the risk of stress corrosion cracking.

TREATMENT: heating of parts at 200°C to 250°C for 2 hours and cooling within the furnace. Validation of stress relief treatment can be performed with the ISO 6957 test.

SOLUBILIZATION OF RESIDUAL β PHASE

After hot stamping, to improve the corrosion resistance of the material, heat treatment between 500°C and 550°C is prescribed for a dwell time at the temperature of at least 2 hours to furnace cooling.

This treatment following the hot stamping operation allows solubilization of the residual beta phase to bring the material to a dezincification-resistant state. The omission of the treatment does not allow the alloy to provide the performance for which it was designed

ALLOY: CW625N

Anti-dezincification alloy with low lead content.

TECHNOLOGICAL PROPERTIES

Structure	Density	Electrical conductivity	Coeff. of thermal expansion	Thermal conductivity*	Specific heat	Elasticity module	Melting point
α	8.5 kg/mm ²	26% IACS	20.5 10 ⁻⁶ K	117 W/(m K)	377 J/(kg K)	103 N/mm ²	880-910 °C

low ○○○○○○ excellent

Machinability: ●●●○○○

Weldability: ●●●●○○

Hot forming: ●●●●○○

Cold Forming: ●●●●○○

Corrosion resistance**: <100 μm

*at room temperature.

**compatibility with chemical substances should be carefully checked.


MECHANICAL PROPERTIES UNI EN12165 ED.2016

Condition of material	Diameter in mm		Hardness HB*	
	from	to (included)	min.	max
M	ALL		AS MANUFACTURED	
H070	8	120	70	150

Special hardness values must be defined when ordering.

Rm N/mm ²	Rp _{0.2} N/mm ²	A%
440-460*	330-360*	24-30*

Values purely indicative.

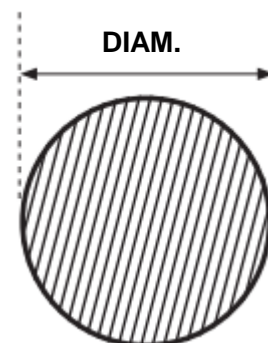

ALLOY: CW625N

Anti-dezincification alloy with low lead content.

DIMENSIONS, TOLERANCES, AND STRAIGHTNESS UNI EN 12165 ED 2016

Nominal diameter (mm)		Tolerances		Diameter (mm)		Length of bar	Tolerance (mm)
		Class A	Class B				
10	18	+/- 0.25	+/- 0.14	10	30	3.0 – 5,0	+/- 100
18	30	+/- 0.30	+/- 0.17	30	50	3.0 – 5,0	+/- 200
30	50	+/- 0.60	+/- 0.20	50	80	3.0	+/- 300
50	80	+/- 0.70	+/- 0.37				
80	120	+/- 2					

The standard "calibrated extruded" product is made in Class B up to and including Ø80 mm. Semi-finished products larger than Ø45 mm can be supplied in the "pressed" and "rolled" forms with Class A tolerance.

Diameter (mm)		Deviation from straightness in mm	
		Every 400 mm	Every m of length L ≥ 1
10	50	0.4	1.0 x L

FINISHING AND PACKAGING

Bar ends	Finishing with saw cut.
Bar surface	Not pickled.
Packaging	1000 kg bundle – 3/5 metal straps. Different bundle packaging and quantities are possible on specific request.
Identification	Adhesive label on strap or bar ends.

ALLOY: CW625N

Anti-dezincification alloy with low lead content.

TECHNICAL NOTES

This alloy was created to limit lead in water for human consumption as much as possible. In addition, arsenic and aluminum significantly reduce dezincification.

The alloy has good hot plastic deformability and good machining characteristics for chip removal. This alloy is designed as a replacement for CW602N for drinking water contact and complies with the requirements of 4MS.